

C28_AJAS_Synthesis_of_Graphene_Oxide

by Wipsar Sunu Brams Dwandaru

Submission date: 11-Dec-2021 10:52PM (UTC+0700)

Submission ID: 1727589351

File name: C28_AJAS_Synthesis_of_Graphene_Oxide.pdf (283.22K)

Word count: 3834

Character count: 20488

Original Research Paper

Synthesis of Graphene Oxide via Liquid Exfoliation Using Self-Custom-Made Tweeter Piezoelectric Ultrasound Generator and Assisted by Surfactant from Commercial Detergent

¹Achmad Ainul Fikri, ¹Aminah Nur Aisyah, ²Suhufa Alfarisa and ¹Wipsar Sunu Brams Dwandaru

¹Department of Physics Education, Universitas Negeri Yogyakarta, Yogyakarta, Indonesia

²Department of Physics, Universitas PGRI Palembang, Palembang, Indonesia

Article history

Received: 17-06-2016

Revised: 23-09-2016

Accepted: 02-11-2016

Corresponding Author:

W.S.B. Dwandaru

Physics Education Department,
Universitas Negeri Yogyakarta,
Yogyakarta, Indonesia

Email: wipsarian@yahoo.com

Abstract: Rapid progress in nanotechnology requires the production of novel nanomaterials. This study aims to synthesize Graphene Oxide (GO) via the Liquid Exfoliation (LE) method using a self-custom-made tweeter piezoelectric system as the ultrasound generator. Linear Alkylbenzena Sulfonate (LAS) surfactant contained in commercial detergent is used to assist the exfoliation process. This synthesis method is simple, inexpensive and may produce GO in a large quantity. Furthermore, the effect of the sonication time on the synthesis of GO is studied. The UV-Vis spectrophotometer and Scanning Electron Microscope (SEM) are used to characterize the synthesis results. UV-Vis analysis shows that the longer the sonication time spent, the thinner the GO layers produced. Moreover, images from SEM show that the surface morphology of the GO forms transparent layers which are stacked together on top of each other.

Keywords: Graphene Oxide, Liquid Exfoliation, Surfactant, Tweeter Piezoelectric Ultrasound Generator

Introduction

Graphene is known as the thinnest and strongest material in the world today which is formed from a single layer of hexagonal honeycomb-shaped carbon atom bounded by covalent bonds (Wang *et al.*, 2013; RSAS, 2010). Many carbon-based materials, such as graphite, carbon nanotube and fullerene are formed by graphene as their basic structure (Basu and Bhattacharyya, 2012). Graphene was first synthesized by Novoselov *et al.* (2004) using the Mechanical Exfoliation (ME) method involving the application of a sticky tape.

Graphene has been an interesting material to be investigated because of its superior properties such as high electron mobility, high conductivity, high thermal conductivity, good optical transparency and high Young's modulus (Terrones *et al.*, 2010). Furthermore, graphene can be applied in various fields such as electronics industry for the manufacture of supercapacitors and transistors (Li *et al.*, 2013; Zhao *et al.*, 2009; El-Kady and Kaner, 2013).

The excitement in graphene leads to the finding of large scale production of graphene layers for the

above mentioned application purposes without losing the above novel properties. One way of achieving this is by graphite oxidation via strong oxidizing agents such that graphite oxide or GO is obtained (Dreyer *et al.*, 2009). Although GO is considered as a forerunner in obtaining graphene, the material itself is being extensively studied for its various uses, such as in biomedical (Chung *et al.*, 2013) and optical (Loh *et al.*, 2010) applications, antibacterial material especially integrated with silver nanoparticles and bacterial cellulose (Zhang *et al.*, 2011; Tang *et al.*, 2013; Shao *et al.*, 2015), bio-sensors (Shao *et al.*, 2010; Liu *et al.*, 2010), hydrogen storage (Wang *et al.*, 2009; Tylanakis *et al.*, 2010; Kim *et al.*, 2012) and filtration membranes (Joshi *et al.*, 2014; Xu *et al.*, 2013).

Many methods has been used in synthesizing graphene or GO. These methods are quite established in various literatures, e.g., ME method (Yi and Shen, 2015), Chemical Vapor Deposition (CVD) (Obraztsov, 2009; Chen *et al.*, 2011), epitaxial growth (Sutter *et al.*, 2008; Yang *et al.*, 2013) and Hummer's method (Reina *et al.*, 2009; Marcano *et al.*, 2010). Another synthesis

method called reduction of Graphene Oxide (rGO) (Stankovich *et al.*, 2007; Pei and Cheng, 2012) is promising due to the large production of graphene, although this method can reduce the electronic performance of graphene (Risley, 2013).

The LE method offers an easier, more efficient and simpler way to synthesize graphene in a large quantity and a good quality (Wang *et al.*, 2016; Hernandez *et al.*, 2008). In this way, surfactant is utilized to assist the exfoliation process of graphene layers from graphite material (Murat *et al.*, 2012). The LE method can produce a stable and good quality of graphene in spite of the defects brought by surfactant (Park and Rouff, 2009; Li *et al.*, 2008). Many researchers then adopted and developed this method in order to optimize the production and quality of graphene or GO. For example, exfoliation of graphite material may be conducted by combining the LE method with electrolysis process (Tang *et al.*, 2012), using kitchen blender (Yi and Shen, 2014), or even sonication (Khan *et al.*, 2010; Bang and Sulick, 2010; Durge *et al.*, 2014).

This study reports the synthesis of GO using the LE method by applying a self-custom-made ultrasound generator consisting of tweeter piezoelectric probes as the ultrasound sources. These probes are used because they are easy to obtain and quite cheap, hence suggesting a reduction in the cost of producing GO. Moreover, they may produce audible and ultrasound frequency range of sound waves which are important in separating graphene layers. Thinner layers of graphene will separate from the thicker ones which are still in the form of cloud-like graphite. The effect of sonication can be directly observed by the increase of the temperature and the change of the solution color into grayish black. Although the use of ultrasound for the exfoliation of graphite or graphite oxide in the LE method is already available in literatures, however, to the knowledge of the authors, the design and use of the ultrasound generator from tweeter piezoelectric probes in this study has not been conducted. Here, the effect of sonication time of the tweeter piezoelectric system towards the synthesis of GO is studied using the UV-Vis spectrophotometer and SEM images.

Meanwhile, LAS surfactants contained in commercial detergents are used to assist the exfoliation process. Surfactants weaken the Van der Waals bond between graphene layers in the graphite material, which is then followed by the separation of graphene layers due to vibrations during the sonication process. By using inexpensive commercial detergents which contain LAS surfactants, the cost of producing GO may be further reduced.

Experimental Method

The main materials employed in this study are (i) graphite powder from Faber-Castell 2B commercial pencil, (ii) commercial detergent containing 20% LAS surfactants and (iii) distilled water. Graphite and detergent powders are illustrated in Fig. 1 (below-right picture). The main equipments utilized are an audio generator (CSi/SPECO SS-1), an amplifier (Uchida TA-2MS) and tweeter piezoelectric probes (Fig. 1 [top and below-left pictures]), which constitute the tweeter piezoelectric ultrasound generator. The ultrasound source apparatus (Fig. 1 top picture) is constructed from a second-hand (used) drinking bottle mounted on a large wooden board as the main pole supporting three piezoelectric probe assemblies which are hanging via flexible cables. Each assembly consists further of three probes (Fig. 1 below-left picture) with each probe attached to the side of a triangle-shaped wooden thinboard.

In the sonication process, each of the assembly is then submerged into the liquid solution sample providing vibrations inside the liquid sample in three directions (Fig. 2 below). Moreover, each of the probes on each assembly may be turned on or off using switches on the large board, such that the number of probes sonicated in the liquid may be varied. On the other hand, the frequency of sound wave in audible and ultrasound ranges may be varied using the audio generator. The results of these two aforementioned variations are being reported elsewhere.

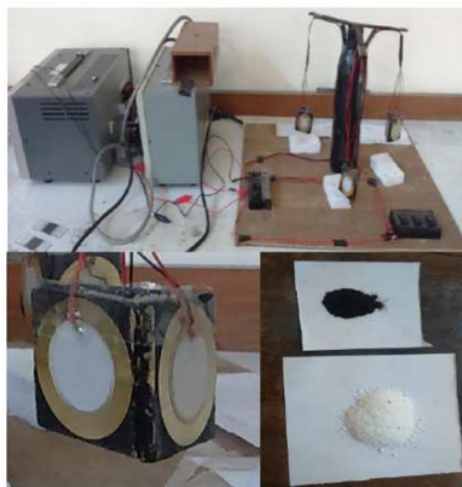


Fig. 1. Tweeter piezoelectric ultrasound generator, consisting of an audio generator, an amplifier and an ultrasound source apparatus (top picture), a tweeter piezoelectric probe assembly (below-left) and graphite (black) and detergent (white) powders [below-right]



Fig. 2. Sonication process of the solution samples

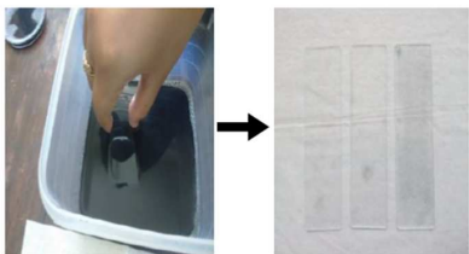


Fig. 3. Dip coating process of the sample from a liquid phase.

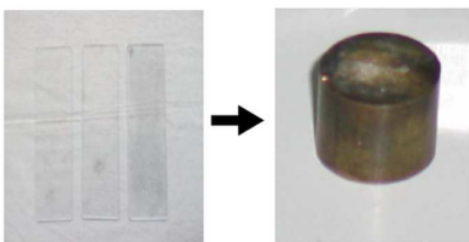


Fig. 4. The solidified sample is moved onto a specimen

The procedures of the experiment in this study are given as follows. Graphite powder as much as 0.5 gram is mixed into a surfactant solution with an amount of 0.025 g mL^{-1} . The surfactant solution is obtained by mixing 200 mL of distilled water with 5 grams of commercial detergent. The prepared graphite solution is then separated into four beaker glasses. Each one of the beaker glasses is sonicated for 1, 3 and 5 h (Fig. 2 above). The last beaker glass is left without sonication process. All of the solutions are then left overnight.

A UV-Visible spectroscopy is conducted upon the supernatant of the solution which has been left overnight. Characterization of the samples is done using a UV-Vis spectrophotometer (Shimadzu UV-2450) in the range of 200 to 700 nm. Moreover, some of the supernatant solution is transferred onto a glass substrate via a dip coating process. Figure 3 shows the dip coating process of the supernatant onto a glass substrate. The

substrate is then annealed in an oven for 10 min at 150°C . Subsequently, SEM (JEOL JSM T300) analysis is conducted at 30 kV for the sample on the substrate (Fig. 4). SEM is performed only for the sample with 5 h sonication time.

Results and Discussion

Liquid Solution Sample after Sonication

The solution sample after sonication may be observed in Fig. 5a. A temperature increase of the solution as a result of sonication is detected as the beaker glass becomes warm (upon touching it) during and right after the sonication process. It may be observed that the color of the solution after the sonication is blue on top of the solution and becomes darker going down to the bottom. Figure 5b shows the solution after it is being left overnight. There is obviously a change in the color of the solution. After being left overnight, the solution becomes grey. There are also dark sediments on the bottom of the solution.

UV-Vis Characterization

Figure 6 shows the UV-Vis result of the samples with 0.025 g mL^{-1} of surfactant and varying sonication time, viz. (in hour): 0, 1, 3 and 5. The graph is obtained by subtracting the UV-Vis absorbance data of the solution from the corresponding absorbance data of the pure surfactant after sonication. The diamond (blue), square (red), triangle (green) and crossed (purple) point data are the absorbance of the sample solutions with 0, 1, 3 and 5 h of sonication time, respectively.

The graphs in Fig. 6 show different absorbance peaks for each sonication time. For 1, 3 and 5 h of sonication time, there are two absorbance peaks which occur at similar wavelengths, i.e.: 270 and 340 nm. However, the absorbance peaks take place in different absorbance values. The absorbance peaks on 270 and 340 nm are characteristics of GO or multilayered graphene (Murat *et al.*, 2012). This is of course different from the absorbance characteristics of the solution without sonication (diamond [blue] data). Without sonication (0 h), the peak on 270 nm is less pronounced, which indicates that the solution may still consist of graphite or graphite oxide.

It may also be observed that as the sonication time spent gets longer, the value of the absorbance peaks decreases. This indicates that the longer the sonication time spent, the thinner the layers of the GO obtained. Moreover, this means that the solution with five hours of sonication time gives the thinnest layers of multilayered graphene. This is evidenced from the lowest peaks of the absorbance at 270 and 340 nm of the crossed (purple) data. This is because the layers of the multilayered graphene undergo more exfoliations as it is exposed to longer time of ultrasound vibrations.

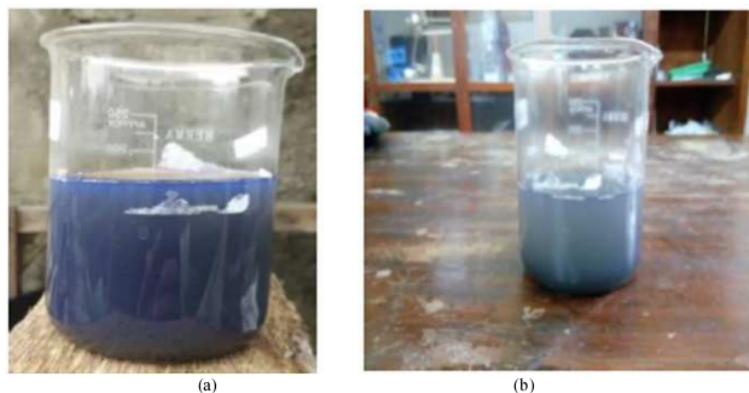


Fig. 5. (a) The solution sample after being sonicated and (b) the solution sample after being left overnight

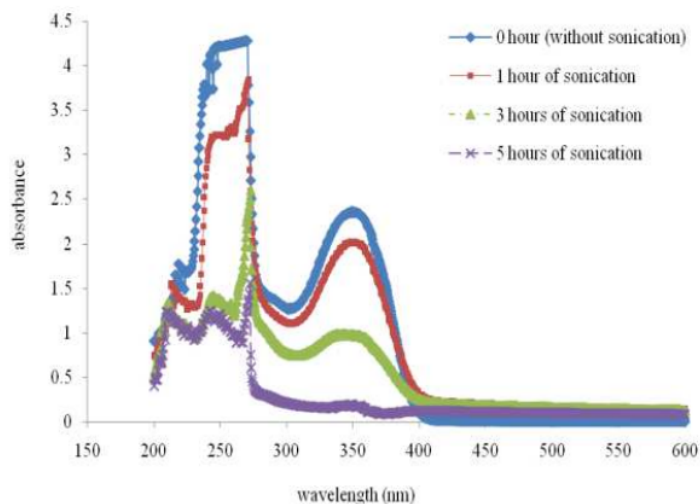


Fig. 6. UV-Vis results of the solution samples with 0.025 g mL^{-1} surfactant and varying sonication time of 0, 1, 3 and 5 h

SEM Results

The SEM analysis is conducted to determine the surface morphology of the material produced. The solution (supernatant) is initially solidified before being characterized using SEM. The supernatant part is solidified by deep coating the glass with the liquid sample solution.

From the UV-Vis result it is obtained that the sample produced with five hours of sonication time gives the most optimize GO's performance (thinnest layers of multi-layered graphene). Therefore, further analysis using SEM is only conducted on that sample. Figure 7 presents the surface morphology of the

solution that undergoes sonication for five hours. Figure 7a displays the solidified material distribution of the sample with 100X magnification. It shows an island of materials on the left-bottom part of the figure. Additionally, smaller materials are scattered throughout the figure with widths ranging from 2.5 to 28 microns. Figure 7b shows cloudlike graphene oxides with 1000X magnification. Layering may also be observed although it is less obvious. Figure 7c illustrates cloud-like graphene oxides with further magnification (2000X) which clearly shows stacking of graphene materials on top of each other. This illustrates that GO is produced in this study.

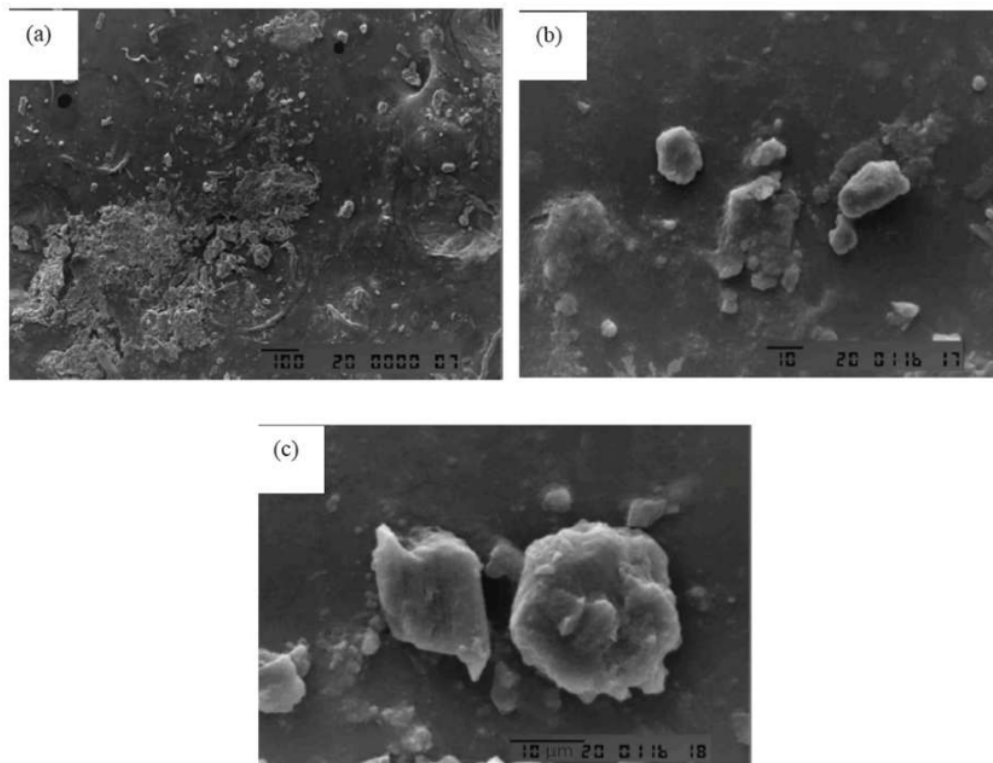


Fig. 7. SEM results for five hours of sonication time taken at different positions on the sample with (a) 100X, (b) 1000X and (c) 2000X magnifications

Conclusion

Synthesis of GO with a simple and inexpensive method of LE has been conducted. Here, the production of GO uses a self-custom-made tweeter piezoelectric ultrasound generator and assisted by LAS surfactant from commercial detergent. The UV-Vis analysis shows that the longer the sonication time spent, the thinner the GO layers produced. SEM results illustrate that the surface morphology of the GO layers consist of transparent layers of graphenes stacked together on top of each other. This study contributes to the many methods in synthesizing GO, especially using simple and inexpensive materials and tools.

Acknowledgement

The authors would also like to express gratitude to Bambang Sugeng, M.Pd., Ph.D for reviewing the language of this article.

Funding Information

This study has been supported by the Faculty of Mathematics and Natural Science of Universitas Negeri Yogyakarta under the funding of DANA DIPA Fakultas MIPA 2016.

Author's Contributions

Achmad Ainul Fikri and Aminah Nur Aisyah: Gave significant contribution in the preparation of this article. They conducted the experiments and data collecting, including assembling the self-custom-made tweeter piezoelectric ultrasound generator. Produced the initial draft of the article.

Suhufa Alfarisa and Wipsar Sunu Brams Dwandaru: Were the supervisors who provided the main idea and oversaw the overall research project, including making sure that the experiments were conducted correctly as planned. Reviewed and finalized the draft of the article before it is being submitted.

References

- Bang, J.H. and K.S. Sulick, 2010. Applications of ultrasound to the synthesis of nanostructured materials. *Adv. Mater.*, 22: 1039-1059. DOI: 10.1002/adma.200904093
- Basu, S. and P. Bhattacharyya, 2012. Recent developments on graphene and graphene oxide based solid state gas sensors. *Sensor Actuators B*, 173: 1-21 DOI: 10.1016/j.snb.2012.07.092
- Chen, Z., W. Ren, L. Gao, B. Liu and S. Pei *et al.*, 2011. Three-dimensional flexible and conductive interconnected graphene networks grown by chemical vapour deposition. *Nat. Mater.*, 10: 424-428. DOI: 10.1038/nmat3001
- Chung, C., Y.K. Kim, D. Shin, S.R. Ryoo and B.H. Hong *et al.*, 2013. Biomedical applications of graphene and graphene oxide. *Acc. Chem. Res.*, 46: 2211-2224 DOI: 10.1021/ar300159f
- Dreyer, D.R., S. Park, C.W. Bielawski and R.S. Rouff, 2010. The chemistry of graphene oxide. *Chem. Soc. Rev.*, 39: 228-240 DOI: 10.1039/b917103g
- Durge, R., R.V. Kshirsagar and P. Tambe, 2014. Effect of sonication energy on the yield of graphene nanosheets by liquid-phase exfoliation of graphene. *Proc. Eng.*, 97: 1457-1465. DOI: 10.1016/j.proeng.2014.12.429
- El-Kady, M.F. and R.B. Kaner, 2013. Scalable fabrication of high-power graphene microsupercapacitors for flexible on-chip energy storage. *Nat. Commun.*, 4: 1475-1475. DOI: 10.1038/ncomms2446
- Hernandez, Y., V. Nicolosi, M. Lotya, F.M. Blighe and Z. Sun *et al.*, 2008. Highyield production of graphene by liquid-phase exfoliation of graphite. *Nat. Nanotechnol.*, 3: 563-568. DOI: 10.1038/nnano.2008.215
- Joshi, R.K., P. Carbone, F.C. Wang, V.G. Kravets and Y. Su *et al.*, 2014. Precise and ultrafast molecular sieving through graphene oxide membranes. *Science*, 343: 752-754 DOI: 10.1126/science.1245711
- Khan, U., A. O'Neill, M. Lotya, S. De and J.N. Coleman, 2010. High-concentration solvent exfoliation of graphene. *Small*, 6: 864-871. DOI: 10.1002/sml.200902066
- Kim, B.H., W.G. Hong, H.Y. Yu, Y.K. Han and S.M. Lee *et al.*, 2012. Thermally modulated multilayered graphene oxide for hydrogen storage. *Phys. Chem. Chem. Phys.*, 14: 1480-1484. DOI: 10.1039/C2CP23683D
- Li, D., M.B. Müller and S. Gilje, 2008. Processable aqueous dispersions of graphene nanosheets. *Nat. Nanotechnol.*, 3: 101-105. DOI: 10.1038/nnano.2007.451
- Li, X., T. Zhao, Q. Chen, P. Li and K. Wang *et al.*, 2013. Flexible all solid-state supercapacitors based on chemical vapor deposition derived graphene fibers. *Phys. Chem. Chem. Phys.*, 15: 17752-17757. DOI: 10.1039/C3CP52908H
- Liu, Y., D. Yu, C. Zheng, Z. Miao and L. Dai, 2010. Biocompatible graphene-oxide based glucose biosensors. *Langmuir*, 26: 6158-6160. DOI: 10.1021/la100886x
- Loh, K.P., Q. Bao, G. Eda and M. Chhowalla, 2010. Graphene oxide as a chemically tunable platform for optical applications. *Nat. Chem.*, 2: 1015-1024. DOI: 10.1038/nchem.907
- Marcano, D.C., D.V. Kosynkin, J.M. Berlin, A. Sinitskii and Z. Sun *et al.*, 2010. Improved synthesis of graphene oxide. *ACS Nano*, 4: 4806-4814. DOI: 10.1021/nn1006368
- Murat, A., J.J. Segura, J. Oro-Sole and N. Casan-Pastor, 2012. The Synthesis of graphene sheets with controlled thickness and order using surfactantassisted electrochemical processes. *Carbon*, 50: 142-152. DOI: 10.1016/j.carbon.2011.07.064
- Novoselov, K.S., A.K. Geim, S.V. Morozov, D. Jiang and Y. Zhang *et al.*, 2004. Electric field effect in atomically thin carbon films. *Science*, 306: 666-669. DOI: 10.1126/science.1102896
- Obraztsov, A.N., 2009. Chemical vapor deposition: making graphene on a large scale. *Nat. Nanotechnol.*, 4: 212-213. DOI: 10.1038/nnano.2009.67
- Park, S. and R.S. Rouff, 2009. Chemical methods for the production of graphenes. *Nat. Nanotechnol.*, 4: 217-224. DOI: 10.1038/nnano.2009.58
- Pei, S. and H.M. Cheng, 2012. The reduction of graphene oxide. *Carbon*, 50: 3210-3228. DOI: 10.1016/j.carbon.2011.11.010
- Reina, A., X. Jia, J. Ho, D. Nezich and H. Son *et al.*, 2009. Large area, few-layer graphene films on arbitrary substrates by chemical vapor deposition. *Nano Lett.*, 9: 30-35 DOI: 10.1021/nl801827v
- Risley, M.J., 2013. Surfactant-assisted solution exfoliation and processing of graphite and graphene. M.Sc. Thesis. School of Chemical and Biomolecular Engineering, Georgia Institute of Technology, Georgia.
- RSAS, 2010. Graphene. Kungliga Vetenskapsakademien, The Royal Swedish Academy of Sciences, Press Release.
- Shao, W., H. Liu, X. Liu, S. Wang and R. Zhang, 2015. Anti-bacterial performances and biocompatibility of bacterial cellulose/graphene oxide composites. *RSC Adv.*, 5: 4795-4803. DOI: 10.1039/C4RA13057J

- Shao, Y., J. Wang, H. Wu, J. Liu and I.A. Aksay *et al.*, 2010. Graphene based electrochemical sensors and biosensors: A review. *Electroanalysis*, 22: 1027-1036. DOI: 10.1002/elan.200900571
- Stankovich, S., D.A. Dikin, R.D. Piner, K.A. Kohlhaas and A. Kleinhammes *et al.*, 2007. Synthesis of graphenebased nanosheets via chemical reduction of exfoliated graphite oxide. *Carbon*, 45: 1558-1565. DOI: 10.1016/j.carbon.2007.02.034
- Sutter, P.W., J.I. Flege and E.A. Sutter, 2008. Epitaxial graphene on ruthenium. *Nat. Mater.*, 7: 406-411. DOI: 10.1038/nmat2166
- Tang, J., Q. Chen, L. Xu, S. Zhang and L. Feng *et al.*, 2013. Graphene-oxidesilver nanocomposite as a highly effective antibacterial agent with species-specific mechanism. *ACS Applied Mater. Interfaces*, 5: 3867-3874. DOI: 10.1021/am4005495
- Tang, L., X. Li, D. Du and C. He, 2012. Fabrication of multilayer films from regenerated cellulose and graphene oxide through layer-by-layer assembly. *Progress Nat. Sci.: Mater. Int.*, 22: 341-346. DOI: 10.1016/j.pnsc.2012.06.005
- Terrones, M., A.R. Botello-Méndez, J. Campos-Delgado, F. López-Urías and Y.I. Vega-Cantú *et al.*, 2010. Graphene and graphite nanoribbons: morphology, properties, synthesis, defects and applications. *Nano Today*, 5: 351-372. DOI: 10.1016/j.nantod.2010.06.010
- Tylianakis, E., G.M. Psfogiannakis and G.E. Froudakis, 2010. Li-doped pillared graphene-oxide: A graphene-based nanostructured material for hydrogen storage. *J. Phys. Chem. Lett.*, 1: 2459-2464. DOI: 10.1021/jz100733z
- Wang, H., X. Yuan, Y. Wu, H. Huang and X. Peng *et al.*, 2013. Graphene-based materials: Fabrication, characterization and application for the decontamination of waste water and waste gas and hydrogen storage/generation. *Adv. Colloid Interface Sci.*, 195-196: 19-40. DOI: 10.1016/j.cis.2013.03.009
- Wang, L., K. Lee, Y.Y. Sun, M. Lucking and Z. Chen *et al.*, 2009. Graphene oxide as an ideal substrate for hydrogen storage. *ACS Nano*, 3: 2995-3000. DOI: 10.1021/nn900667s
- Wang, S., M. Yi and Z. Shen, 2016. The effect of surfactants and their concentrations on the liquid-exfoliation of graphene. *RSC Adv.*, 6: 56705-56710. DOI: 10.1039/C6RA10933K
- Xu, C., A. Cui, Y. Xu and X. Fu, 2013. Graphene oxide-TiO₂ composite filtration membranes and their potential application for water purification. *Carbon*, 62: 465-471. DOI: 10.1016/j.carbon.2013.06.035
- Yang, W., G. Chen, Z. Shi, C.C. Liu and L. Zhang *et al.*, 2013. Epitaxial growth of single-domain graphene on hexagonal boron nitride. *Nat. Mater.*, 12: 792-797. DOI: 10.1038/nmat3695
- Yi, M. and Z. Shen, 2014. Kitchen blender for producing high-quality few-layer graphene. *Carbon*, 78: 622-626. DOI: 10.1016/j.carbon.2014.07.035
- Yi, M. and Z. Shen, 2015. A review on mechanical exfoliation for the scalable production of graphene. *J. Mater. Chem. A*, 3: 11700-11715. DOI: 10.1039/C5TA00252D
- Zhang, D., X. Liu and X. Wang, 2011. Green synthesis of graphene oxide sheets decorated by silver nanoprisms and their anti-bacterial properties. *J. Inorganic Biochem.*, 105: 1181-1186. DOI: 10.1016/j.jinorgbio.2011.05.014
- Zhao, L., L. Zhao, Y. Xu, T. Qiu and L. Zhi *et al.*, 2009. Polyaniline electrochromic devices with transparent graphene electrodes. *Electrochimica Acta*, 55: 491-497. DOI: 10.1016/j.electacta.2009.08.063

C28_AJAS_Synthesis_of_Graphene_Oxide

ORIGINALITY REPORT

21 %
SIMILARITY INDEX

18 %
INTERNET SOURCES

9 %
PUBLICATIONS

3 %
STUDENT PAPERS

PRIMARY SOURCES

1 www.thescipub.com 10 %
Internet Source

2 pendidikan-fisika.fmipa.uny.ac.id 2 %
Internet Source

3 "Inorganic Nanosheets and Nanosheet-Based Materials", Springer Science and Business Media LLC, 2017 1 %
Publication

4 Submitted to Multimedia University 1 %
Student Paper

5 Wipsar Sunu Brams Dwandaru, Lia Desi Parwati, Rhyko Irawan Wisnuwijaya. "Formation of graphene oxide from carbon rods of zinc-carbon battery wastes by audiosonic sonication assisted by commercial detergent", Nanotechnology and Precision Engineering, 2019 1 %
Publication

6 www.frontiersin.org 1 %
Internet Source

7	Submitted to Universiti Sains Malaysia Student Paper	1 %
8	Submitted to Muscat College Student Paper	<1 %
9	link.springer.com Internet Source	<1 %
10	Yu, Jin-Gang, Lin-Yan Yu, Hua Yang, Qi Liu, Xiao-Hong Chen, Xin-Yu Jiang, Xiao-Qing Chen, and Fei-Peng Jiao. "Graphene nanosheets as novel adsorbents in adsorption, preconcentration and removal of gases, organic compounds and metal ions", The Science of The Total Environment, 2015. Publication	<1 %
11	dr.ntu.edu.sg Internet Source	<1 %
12	iopscience.iop.org Internet Source	<1 %
13	Chaoliang Tan, Xiehong Cao, Xue-Jun Wu, Qiyuan He et al. "Recent Advances in Ultrathin Two-Dimensional Nanomaterials", Chemical Reviews, 2017 Publication	<1 %
14	Irina Skorobogatykh, Daria Malova, Zhanna Musatova, Ekaterina Agalarova. "Marketing Management of Sustainable Development of	<1 %

Territories in Russia", American Journal of Applied Sciences, 2016

Publication

15

Oscar Bagoole, Md Mahfuzur Rahman, Sohail Shah, Haiping Hong, Hang Chen, Amal Al Ghaferi, Hammad Younes. "Functionalized three-dimensional graphene sponges for highly efficient crude and diesel oil adsorption", Environmental Science and Pollution Research, 2018

Publication

<1 %

16

"Sonochemical Preparation of Graphene Nanocomposites: Process Intensification", Chemical Functionalization of Carbon Nanomaterials, 2015.

Publication

<1 %

17

Chen, Minjie, Junfa Yin, Yong Liang, Shaopeng Yuan, Fengbang Wang, Maoyong Song, and Hailin Wang. "Oxidative stress and immunotoxicity induced by graphene oxide in zebrafish", Aquatic Toxicology, 2016.

Publication

<1 %

18

Rhyko Irawan Wisnuwijaya, Agus Purwanto, Wipsar Sunu Brams Dwandaru. "UV-Visible Optical Absorbance of Graphene Oxide Synthesized from Zinc-Carbon Battery Waste via a Custom-Made Ultrasound Generator

<1 %

based on Liquid Sonication Exfoliation Method", Makara Journal of Science, 2017

Publication

19

Xiaoya Yuan. "Enhanced interfacial interaction for effective reinforcement of poly(vinyl alcohol) nanocomposites at low loading of graphene", Polymer Bulletin, 2011

Publication

<1 %

20

aip.scitation.org

Internet Source

<1 %

21

dspace.sctimst.ac.in

Internet Source

<1 %

22

pure.ulster.ac.uk

Internet Source

<1 %

23

Julio R. Pinzón. "Fullerenes, Carbon Nanotubes, and Graphene for Molecular Electronics", Topics in Current Chemistry, 2011

Publication

<1 %

Exclude quotes Off

Exclude matches Off

Exclude bibliography On

C28_AJAS_Synthesis_of_Graphene_Oxide

GRADEMARK REPORT

FINAL GRADE

/100

GENERAL COMMENTS

Instructor

PAGE 1

PAGE 2

PAGE 3

PAGE 4

PAGE 5

PAGE 6

PAGE 7
